

International Journal of Pavement Engineering

2018 Impact Factor
2.298

[Publish open access in this journal](#)

[Advanced search](#)


[Submit an article](#) [New content alerts](#) [RSS](#) [Subscribe](#) [Citation search](#)

[Current issue](#) [Browse list of issues](#) [Explore](#)

Endorsed by the International Society for Concrete Pavements

This journal



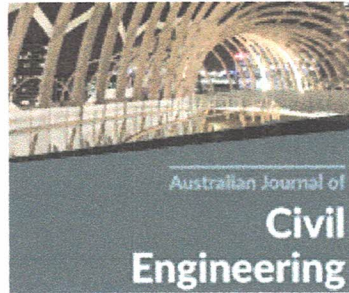

Latest articles

Article

Experimental investigation surface abrasion resistance and surface frost resistance of concrete pavement incorporating fly ash and slag >

Xu et al.
Published online: 17 Feb 2020

Article

Theoretical and practical engineering significance of British pendulum test >

Chu et al.
Published online: 17 Feb 2020

Article

Evaluation of natural asphalt properties treated with egg shell waste and low density polyethylene >

Nejres et al.
Published online: 17 Feb 2020

Article

Organic-based recycling agents for road paving applications in cold-climate regions >

Ashimova et al.
Published online: 14 Feb 2020

[View more >](#)

[See all volumes and issues](#)

< **Volume 21, 2020** Vol 20, 2019 Vol 1 >

< Issue 3 Issue 2 Issue 1 >

 [Download citations](#)

Original Articles

 Article
[Numerical analysis for widening embankments over soft soils treated by PVD and DJM columns](#) >

Xin Jiang, Yi Jiang, Chao-Yang Wu, Wen-Qi Wang, Jian-Yu Geng & Yan-Jun Qiu

Pages: 267-279

Published online: 30 Apr 2018

102 1 0
Views CrossRef citations Altmetric

Articles

 Article
[Effects of layer interface conditions on top-down fatigue cracking of asphalt pavements](#) >

Mohsen Alae, Yanqing Zhao, Sohrab Zarei, Guozhi Fu & Dandan Cao

Pages: 280-288

Published online: 19 Apr 2018

239 1 0
Views CrossRef citations Altmetric

Original Articles

 Article
[Impact of vibration compaction on the paving density and transverse uniformity of hot paving layer](#) >

Jie Jia, Honghai Liu, Yipin Wan & Kailong Qi

Pages: 289-303

Published online: 30 Apr 2018

100 1 0
Views CrossRef citations Altmetric

Articles


Article
 [Layer coefficients of cold in-place recycled layers from performance data >](#)

Irvin Pinto & Ashley Buss

Pages: 304-310

Published online: 25 May 2018

63 1 0
Views CrossRef citations Altmetric

Article
 [An investigation towards intelligent tyres using finite element analysis >](#)

Pooya Behroozinia, Seyedmeysam Khaleghian, Saied Taheri & Reza Mirzaeifar

Pages: 311-321

Published online: 24 May 2018

123 1 0
Views CrossRef citations Altmetric

Article
 [Impact of water and solution of glycerol on the treatment of sediment by cement >](#)

A. R. Estabragh, M. Kouchakzadeh & A. A. Javadi

Pages: 322-335

Published online: 24 May 2018

48 0 0
Views CrossRef citations Altmetric

Article
 [Performance evaluation of semi-flexible permeable pavements under cyclic loads >](#)

Mahdi M. Disfani, Alireza Mohammadinia, Guillermo A. Narsilio & Lu Aye

Pages: 336-346

Published online: 23 May 2018

174 Views 4 CrossRef citations 0 Altmetric

Article



[Stress dependent and redistribution behaviour of unbound granular material >](#)

Shaohui Li & Peiwen Hao

Pages: 347-356

Published online: 23 May 2018

101 Views 0 CrossRef citations 0 Altmetric

Article



[Back analysis of the multilayer cylindrical HMA samples – height reduction method >](#)

A. Pożarycki, P. Górnaś, P. Rydzewski & D. Wanatowski

Pages: 357-364

Published online: 01 Jun 2018

88 Views 0 CrossRef citations 0 Altmetric

Article



[Finite element modelling of the rolling resistance due to pavement deformation >](#)

Gabriel Bazi, Elie Y. Hajj, Alvaro Ulloa-Calderon & Per Ullidtz

Pages: 365-375

Published online: 05 Jun 2018

145 Views 2 CrossRef citations 0 Altmetric

Article

An approach to mitigate effects of colour variation, specularity and pores on microtexture analysis of aggregates >

Abolfazl Ravanshad, Sanghyun Chun, Reynaldo Roque & George Lopp

Pages: 376-383

Published online: 30 May 2018

30	0	0
Views	CrossRef citations	Altmetric

Article

Probabilistic approach to characterise laboratory rutting behaviour of asphalt concrete mixtures >

Priyansh Singh & Aravind Krishna Swamy

Pages: 384-396

Published online: 08 Jun 2018

128	0	0
Views	CrossRef citations	Altmetric

Article

Performance characteristics of epoxy asphalt paving material for thin orthotropic steel plate decks >

Can Chen, Wolfgang O. Eisenhut, Kreisler Lau, Ashley Buss & John Bors

Pages: 397-407

Published online: 18 Jun 2018

132	3	0
Views	CrossRef citations	Altmetric

Explore

[Most read articles](#)[Most cited articles](#)[6 Open access articles](#)

Article
Examination of moisture sensitivity of aggregate-bitumen bonding strength using loose asphalt mixture and physico-chemical surface energy property tests >

Article
Optimisation of pavement maintenance and rehabilitation activities, timing and work zones for short survey sections and multiple distress types >

Article
A laboratory procedure for predicting skid and polishing resistance of road surfaces >

Article
Mechanical and structural assessment of laboratory- and field-compacted asphalt mixtures >

Liu et al.
 Volume 15, 2014 - Issue 7
Published online: 25 Mar 2014
 Views: 4297



Donev et al.
 Latest Articles
Published online: 24 Jul 2018
 Views: 2294



Hofko et al.
 Volume 20, 2019 - Issue 4
Published online: 4 Apr 2017
 Views: 2245



Airey et al.
 Volume 17, 2016 - Issue 1
Published online: 16 Jun 2014
 Views: 1919



[View more >](#)



Journal

International Journal of Pavement Engineering >

This journal

Editorial board

Co-Editors-in-Chief:

Tom Scarpas - *Section of Structural Mechanics, Faculty of Civil Engineering & Geosciences, Delft University of Technology, Stevinweg 1, 2628 CN Delft, The Netherlands.*

Imad L. Al-Qadi - *Dept of Civil and Environmental Eng., MC 250, 205 N. Mathews Ave, University of Illinois at Urbana-Champaign, Urbana, Illinois 61801, USA.*

Associate Editors:

Amit Bhasin - *The University of Texas at Austin, USA*

Ronald Blab - *Technische Universitat Wien, Austria*

Navneet Garg - *Federal Aviation Administration, USA*

Elie Hajj - *University of Nevada, Reno, USA*

Theuns F. P. Henning - *The University of Auckland, New Zealand*

Lev Khazanovich - *University of Minnesota, USA*

M. Emin Kutay - *Michigan State University, USA*

Sabine Leischner - *Dresden University of Technology, Germany*

Luis Loria-Salazar - *University of Costa Rica, Costa Rica*

Andreas Loizos - *National Technical University of Athens, Greece*

J. Murali Krishnan - *Indian Institute of Technology Madras, India*

Eyad Masad - *Texas A&M University, USA*

Anand Puppala - *The University of Texas at Arlington, USA*

Hasan Ozer - *University of Illinois, USA*

Jeff Roesler - *University of Illinois at Urbana - Champaign*

Omar Smadi - *Iowa State University, USA*

Wynand Steyn - *University of Pretoria, South Africa*

Editorial Board:

Khaled Abaza - *Birzeit University, Palestine*

Armen Amirkhanyan - *University of Alabama, USA*

José Tadeu Balbo - *University of São Paulo, Brazil*

Amit Bhasin - *University of Texas at Austin, USA*

Bjorn Birgisson - *Aston University, UK*

Ronald Blab - *TU Wien -Institute of Transportation, Austria*

Alex Brand - *Virginia Tech, USA*

Neeraj Buch - *Michigan State University at East Lansing, USA*

Silvia Caro - *Universidad de los Andes, Colombia*

Karim Chatti - *Michigan State University at East Lansing, USA*

Ghassan Chehab - *American University of Beirut, Lebanon*

Joe Daniel - *University of New Hampshire*

Michael I. Darter - *Applied Research Associates, Inc., Champaign, USA*

Andrew Dawson - *University of Nottingham, UK*

Mostafa Elseifi - *Louisiana State University, USA*

Sandra Erkens - *Delft University of Technology, The Netherlands*

Fwa Tien Fang - *National University of Singapore, Singapore*

Decheng Feng - *Harbin Institute of Technology, China*

Gerardo Flintsch - *Virginia Polytechnic Institute and State University, USA*

Navneet Garg - *Federal Aviation Administration, USA*

Elie Hajj - *University of Nevada Reno, USA*

John T. Harvey - *University of California Pavement Research Center, USA*

Theuns Henning - *The University of Auckland, New Zealand*

Lambert Houben - *Delft University of Technology, The Netherlands*

Malal Kane - *LCPC, France*

Lev Khazanovich - *University of Pittsburgh, USA*

Yong-Rak Kim - *University of Nebraska-Lincoln, USA*

Emin Kutay - *Michigan State University, USA*

Pyeong Jun Yoo - *Korea Institute of Construction Technology, Republic of Korea*

Sabine Leischner - *Technische Universität Dresden, Germany*

Dallas Little - *Texas A&M University, USA*

Andreas Loizos - *National Technical University of Athens, Greece*

Luis Loria-Salazar - *Universidad de Costa Rica, Costa Rica*

Massimo Losa - *University of Pisa*

Gulay Malkoc - *Turkish Asphalt Contractors Association, Turkey*

Eyad Masad - *Texas A&M University, USA*

Krishnan Murali - *Indian Institute of Technology Madras, India*

Atal Narayan - *Indian Institute of Technology Madras, India*

Sohail Nazarian - *University of Texas, USA*

Markus Oeser - *RWTH Aachen University, Germany*

Hasan Ozer - *Arizona State University, USA*

Troy Pauli - *Western Research Institute, USA*

Luis Picado Santos - *University of Lisbon*

Christina Plati - *National Technical University of Athens, Greece*

Anand Puppala - *Texas A&M University, USA*

Kumbakonam Rajagopal - *Texas A&M University, USA*

Ezio Santagata - *University of Torino, Italy*

Chuck Schwartz - *University of Maryland, USA*

Omar Smadi - *Iowa State University, USA*

Mark Snyder - *Independent Consultant*

Wynand Steyn - *University of Pretoria, South Africa*

Alessandro Di Graziano - *Department of Civil Engineering and Architecture, University of Catania*

Aravind Swamy - *Indian Institute of Technology-Delhi, India*


Shiraz D. Tayabji - *CTL Group, Maryland, USA*

Susan Tighe - *University of Waterloo, Canada*

Erol Tutumluer - *University of Illinois, USA*

**Sample Our
Engineering & Technology
journals**



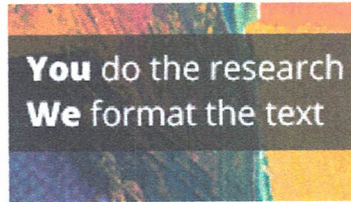

Format-free submission.
Click here for more info →

Information for

[Authors](#)

[Editors](#)

[Librarians](#)

[Societies](#)

Open access

[Overview](#)

[Open journals](#)

[Open Select](#)

[Cogent OA](#)

Help and info

[Help & contact](#)

[Newsroom](#)

[Commercial services](#)

[All journals](#)

Keep up to date

Register to receive personalised research and resources by email



[Sign me up](#)




Copyright © 2020 Informa UK Limited [Privacy policy](#) [Cookies](#) [Terms & conditions](#) [Accessibility](#)

Registered in England & Wales No. 3099067
5 Howick Place | London | SW1P 1WG

 **Download citations**

Articles


Article
 **Effect of input source energy and measurement of flexible pavement deflection using the SASW method** >

Norfarah Nadia Ismail, Nur Izzi Md. Yusoff, Khairul Anuar Mohd Nayan, Norinah Abd Rahman, **Sri Atmaja P. Rosyidi** & Amiruddin Ismail

Pages: 382-392

Published online: 10 Mar 2017

187 0 0
Views CrossRef citations Altmetric


Article
 **Developing performance models for treated gravel roads to evaluate the cost-effectiveness of using dust chemical treatments** >

Mohammed Ali Okok, Promotes Saha & Khaled Ksaibati

Pages: 393-401

Published online: 29 Mar 2017

184 4 0
Views CrossRef citations Altmetric

Article
 **Statistical evaluation of factors affecting the laboratory rutting susceptibility of asphalt mixtures** >

Sabahat Hussan, Mumtaz Ahmed Kamal, Imran Hafeez, Danish Farooq, Naveed Ahmad & Shahab Khanzada

Pages: 402-416

Published online: 08 Mar 2017

430 6 0
Views CrossRef citations Altmetric

Article

[Evaluation of cracking in asphalt pavement with stabilized base course based on statistical pattern recognition >](#)

Qun Yang & Yingjie Deng

Pages: 417-424

Published online: 07 Mar 2017

311 Views 3 CrossRef citations 0 Altmetric

Article

[Maintenance of airport pavements: the use of visual inspection and IRI in the definition of degradation trends >](#)

Ana Filipa Carreiro Carvalho & Luís Guilherme de Picado Santos

Pages: 425-431

Published online: 10 Apr 2017

267 Views 3 CrossRef citations 0 Altmetric

Article

[Improving the resilient modulus of a gypsum sand roadbed soil by increased compaction >](#)

Sabah Said Razouki & Ali Nasir Ibrahim

Pages: 432-438

Published online: 06 Apr 2017

223 Views 3 CrossRef citations 0 Altmetric

Article

[A laboratory procedure for predicting skid and polishing resistance of road surfaces >](#)

Bernhard Hofko, Hannes Kugler, Georgi Chankov & Roland Spielhofer

Pages: 439-447

Published online: 04 Apr 2017

2245 2 0
Views CrossRef citations Altmetric



Article

Freeze–thaw resistance assessment of cement-bound steel slag aggregate for pavement structures >

Ivana Barišić, Berislav Marković & Martina Zagvozda

Pages: 448-457

Published online: 08 Apr 2017

212 1 0
Views CrossRef citations Altmetric

Article

Detecting road pavement deterioration with finite mixture models >

Kristin Svenson, Stuart McRobbie & Moudud Alam

Pages: 458-465

Published online: 10 Apr 2017

179 0 0
Views CrossRef citations Altmetric

Article

Terrestrial laser scanner for the analysis of airport pavement geometry >

Maurizio Barbarella, Maria Rosaria De Blasiis & Margherita Fiani

Pages: 466-480

Published online: 08 Apr 2017

179 3 0
Views CrossRef citations Altmetric

Article

A functional approach for determining skid resistance threshold state of porous pavement >

L. J. Chu & T. F. Fwa

Pages: 481-489

Published online: 10 Apr 2017

354 Views 1 CrossRef citations 0 Altmetric

Article

Development of ANN-GA program for backcalculation of pavement moduli under FWD testing with viscoelastic and nonlinear parameters >

Maoyun Li & Hao Wang

Pages: 490-498

Published online: 09 Apr 2017

404 Views 5 CrossRef citations 0 Altmetric

Article

Evaluation of aging performance of bitumen containing layered double hydroxides intercalated by UV absorbents >

Song Xu, Jianying Yu, Changbin Hu, Lijuan Jia & Lihui Xue

Pages: 499-505

Published online: 12 Apr 2017

143 Views 2 CrossRef citations 0 Altmetric

Explore

Most read articles

Most cited articles

6 Open access articles

Article
Examination of moisture sensitivity of aggregate-bitumen bonding strength using loose asphalt mixture and physico-chemical surface energy property tests >

Article
Optimisation of pavement maintenance and rehabilitation activities, timing and work zones for short survey sections and multiple distress types >

Article
A laboratory procedure for predicting skid and polishing resistance of road surfaces >

Article
Mechanical and structural assessment of laboratory- and field-compacted asphalt mixtures >

Liu et al.
 Volume 15, 2014 - Issue 7
Published online: 25 Mar 2014
 Views: 4297



Donev et al.
 Latest Articles
Published online: 24 Jul 2018
 Views: 2294



Hofko et al.
 Volume 20, 2019 - Issue 4
Published online: 4 Apr 2017
 Views: 2245



Airey et al.
 Volume 17, 2016 - Issue 1
Published online: 16 Jun 2014
 Views: 1919



[View more >](#)

Information for

[Authors](#)

[Editors](#)

[Librarians](#)

[Societies](#)

Open access

[Overview](#)

[Open journals](#)

[Open Select](#)

[Cogent OA](#)

Help and info

[Help & contact](#)

[Newsroom](#)

[Commercial services](#)

[All journals](#)

Keep up to date

Register to receive personalised research and resources by email



[Sign me up](#)



[Copyright © 2020 Informa UK Limited](#) [Privacy policy](#) [Cookies](#) [Terms & conditions](#) [Accessibility](#)

Registered in England & Wales No. 3099067
5 Howick Place London SW1P 1WG



Effect of input source energy and measurement of flexible pavement deflection using the SASW method

Norfarah Nadia Ismail, Nur Izzu Md. Yusoff, Khairul Anuar Mohd Nayan, Norinah Abd Rahman, Sri Atmaja P. Rosyidi & Amiruddin Ismail

To cite this article: Norfarah Nadia Ismail, Nur Izzu Md. Yusoff, Khairul Anuar Mohd Nayan, Norinah Abd Rahman, Sri Atmaja P. Rosyidi & Amiruddin Ismail (2019) Effect of input source energy and measurement of flexible pavement deflection using the SASW method, International Journal of Pavement Engineering, 20:4, 382-392, DOI: [10.1080/10298436.2017.1298104](https://doi.org/10.1080/10298436.2017.1298104)

To link to this article: <https://doi.org/10.1080/10298436.2017.1298104>



Published online: 10 Mar 2017.



Submit your article to this journal [↗](#)




Article views: 55



View Crossmark data [↗](#)

Effect of input source energy and measurement of flexible pavement deflection using the SASW method

Norfarah Nadia Ismail^a, Nur Izzi Md. Yusoff^a, Khairul Anuar Mohd Nayan^a, Norinah Abd Rahman^a, Sri Atmaja P. Rosyidi^b and Amiruddin Ismail^a 

^aDepartment of Civil and Structural Engineering, Universiti Kebangsaan Malaysia, Selangor, Malaysia; ^bDepartment of Civil and Structural Engineering, Universitas Muhammadiyah Yogyakarta, Yogyakarta, Indonesia

ABSTRACT

This paper presents the effect of input source energy on the results of spectral analysis of surface wave (SASW) evaluation of flexible pavements in terms of maximum and minimum wavelength. A series of surface wave tests, namely the SASW test, were done on asphalt pavement using four steel balls with different masses as sources. These sources were dropped from two different heights, 0.25 and 0.50 m. This test was also conducted with two different configurations, i.e. with the receivers positioned 0.15 and 0.30 m apart. This paper also presents the feasibility of using accelerometers to measure flexible pavement deflection. For this purpose, the process of integrating accelerometer time history is described. It is proved that a change in input source energy has some effect on the value of maximum and minimum wavelength. The result for numerical double integration is satisfactory and is congruent with the displacement obtained through finite element analysis.

ARTICLE HISTORY

Received 20 September 2016
Accepted 19 February 2017

KEYWORDS

Spectral analysis of surface wave; non-destructive test; accelerometer; numerical integration; road deflection

1. Introduction

The use of surface wave in seismic testing has gained popularity in engineering practice as a method for determining shear wave velocity profile (Stokoe *et al.* 2004, Lin and Lin 2007). The surface wave testing in engineering, which have been used quite extensively for quite some time, is associated with the two-station set-up used in the spectral analysis of surface wave (SASW) method (Kausel and Roesset 1981, Nazarian *et al.* 1988, Rix and Stokoe 1989, Gucunski and Woods 1991, Nazarian and Desai 1993). The systematic introduction of the seismic surface wave method to engineering applications has resulted in an increased use of this non-destructive testing technology (Nazarian and Stokoe 1986). In general, SASW has been widely used as a non-destructive test for evaluating subsurface parameters in soils and pavements. SASW utilises Rayleigh waves which propagate at different velocities depending on frequency. The dispersive characteristics of Rayleigh waves propagating through a layered material were measured and were then used to delineate the modulus profile of a pavement section and also to evaluate the S-wave profile of the material (Stokoe *et al.* 1994, Stokoe *et al.* 2004). Dispersion curve is a plot of variation in Rayleigh wave phase velocity against wavelength or frequency (Kumar and Naskar 2015).

The SASW method is a simple technique which could be easily implemented in the field. It has a source–receiver configuration with multiple sources which are carefully selected for the measured wavelength range of each source–receiver configuration,

and therefore provide high-quality results. Phase velocities are calculated from the phase difference. The key feature of SASW method is that it measures apparent velocities, which correspond to the superposed mode of higher mode surface waves and body waves. Determination of apparent phase velocities incorporates phase unwrapping. The phase unwrapping procedure often requires experienced personnel making the best decision during the unwrapping process. However, the non-systematic nature of unwrapping a phase could be improved with a signal processing technique, such as the impulse response filtration technique (Joh *et al.* 1997) and Gabor spectrum.

SASW is capable of accurately defining the elastic moduli and the thickness of layered systems, such as soil and pavement, with a particular advantage of it being performed entirely on the surface (Gucunski and Woods 1992). In general, waves travel at high velocity (and high frequency) in pavement materials. It is known that the higher frequency waves are associated with shorter wavelength and, as a result, these waves propagate only at shallow depths. On the other hand, lower frequency waves have longer wavelength and travel through deeper layers (Jones 1962, Heisey *et al.* 1982, Nazarian 1984). For asphalt pavements, the ground is excited using a small impact source to generate waves propagating at shallow depth. Roesset *et al.* (2011) stated that: (1) an increase in the height of the dropping mass lead to an increase in impact velocity and contact force; and (2) an increase in the dropping mass results in an amplification of the low frequency components of the Fourier Spectrum of the contact force (Kumar and Naskar 2015).

Very recently, several studies were conducted to evaluate pavements using the SASW method through the use of a spherical mass dropped from different heights (Kumar 2011, Kumar and Rakaraddi 2012, Kumar and Rakaraddi 2013a, 2013b, Kumar and Hazra 2014a, 2014b, Kumar and Naskar 2015). A study on concrete pavements conducted by Kumar and Hazra in 2014 found that the value of maximum and minimum wavelength is a function of the magnitude of the input source energy. The researchers also confirmed the usefulness of SASW technique in exploring the shear wave velocity profiles of different pavement layers. In 2012, Kumar and Rakaraddi revealed that there is a need to consider the height of fall of dropping weight in SASW testing. Their 2013 research showed that the distance between the source and first receiver for cement concrete pavements should be greater than the distance for asphaltic pavements. Their finding showed that the acceptable distance for tests on asphaltic pavements is 0.5–0.75 m. This paper improves the findings of these studies, in that this study was applied to the condition of asphaltic pavement in Malaysia, with the recommendation and addition of variation in receiver distance.

This study was also conducted to investigate the feasibility of using accelerometers to measure road deflection. Measurement of road deflection due to traffic loading always requires complex installation of sensors and is often regarded as a trivial job. This paper proposed the use of accelerometers as a small yet reliable sensor to measure road deflection by performing numerical double integration. Currently, other than geophones, accelerometers are one of the devices widely used to obtain either dynamic measurements, which are mainly used to measure track deflection (Hall 2003, Bowness *et al.* 2007, Priest and Powrie 2009, Jiang, Bian, Cheng, *et al.* 2016, Jiang, Bian, Jiang, *et al.* 2016, Sayeed and Shaheen 2016), or static measurement, such as bridge deflection (Roberts *et al.* 2001) and road deflection (Arraigada and Partl 2006, Simonin *et al.* 2009). The installation of the sensors is practical and easy, with the robust POLLCA hardware providing a lot of advantage due to its handling mobility and portability. The use of POLLCA could be a low-cost solution for the measurement of road deflection in industry.

From this measurement, the recorded time series were used to measure deflection. This paper shows the feasibility of using the measurement obtained from using accelerometers to measure road deflection. According to Simonin *et al.* (2009), road deflection measurement is the first element in evaluating road bearing capacity. The measurement level, however, quickly changes along the roadway. Thus, the placement of the measurement device (in this case, accelerometer) on road surface is crucial to ensure accurate results.

2. Methodology

A series of field tests were carried out to investigate the effect of input energy on SASW evaluation in terms of maximum and minimum wavelength. The SASW method makes use of the determination of phase difference between two receivers over a wide range of frequencies. With regard to data collection for the experiment, the equipment and testing configuration used in this test is closely related to the scope of the test and the technique to be used in the interpretation of the results. In order to determine the length of the measurement, the desired depth of

investigation must always be taken into account. The relationship between frequency, wavelength and phase velocity makes the frequency range of interest closely related to the materials to be investigated. For example, deep penetration in soft soils requires lower frequency components (Roesset 1998). Therefore, preliminary information, or 'a-priori' knowledge, regarding the site being investigated is very helpful.

2.1. Testing equipment

The basic equipment used in the SASW test comprised of receivers (accelerometers) connected to an acquisition device which digitises and stores seismic signals. The desired depth of penetration will determine the appropriate type of receivers and the specifications required. Various types of recording equipments, the main function of which is to digitise and record analog electric signals generated by the receivers, could be used. The use of digital signal analyzer allows signal to be processed in real-time, therefore quality assessment and preliminary interpretation could be performed instantly on site. In this test, data were recorded using a Portable Outdoor Laptop with a Customized Compact Analyzer (POLCCA). It is a portable field laptop with built-in dynamic signal analyzer. In this test, which was done on asphalt pavement, steel balls 25.4, 38.1, 50.8 and 76.2 mm in diameters were used.

2.1.1. Sources in SASW Testing

Several sources were used in the SASW testing to excite the ground, induce vibration and produce waves which travel through the layered systems (in this case the asphaltic pavement). Different types of sources can be used, which range from ordinary hammers to expensive controlled source. Controlled sources allow for the collection of high-quality data with high signal to noise ratio.

Sources are typically applied by dropping weights of different sizes (Roesset 1998). For further source offset which requires longer frequency range to penetrate deeper into the ground, an ordinary impact hammer might not be sufficient. Therefore, heavier sources are required. In this test, the sources used were four steel balls with varying mass and diameter, as shown in Figure 1.

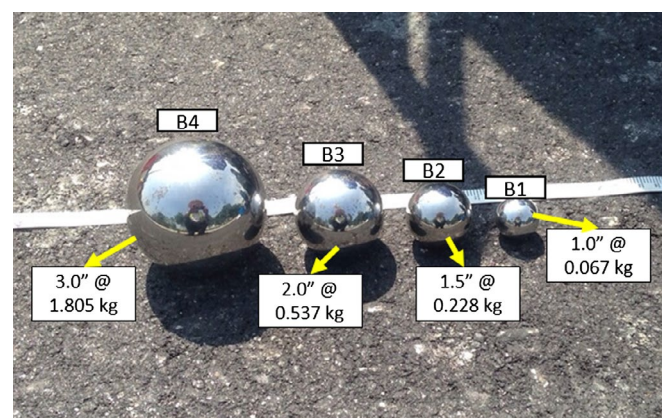


Figure 1. Steel balls with different diameters and masses, m used in the test.

Table 1. Characteristics of the accelerometer according to manufacturer's specification.

Series	352C68
Sensitivity ($\pm 10\%$)	100 mV/g
Measurement range	50 g pk
Frequency range ($\pm 10\%$)	0.3–12,000 Hz
Resonant frequency	≥ 35 kHz
Spectral noise (10 Hz)	16 $\mu\text{g}/\sqrt{\text{Hz}}$

2.1.2. Sensors

In order to choose an appropriate sensor with the desired specification, it is necessary to relate it with the desired depth of penetration. The typical frequency range for pavements is between 1000 and 15,000 Hz, and this makes accelerometers the best sensors for measurement on pavements as it has higher resonance frequency compared to geophones.

For pavement testing where the frequency range is of particular interest, or when testing stiffer materials where the desired depth is shallow, accelerometers are typically used as receivers. Accelerometers can reach operative frequencies in the kHz range and as with any other types of dynamic sensors, data can be synthesised in the time or frequency domain. Accelerometers are for the most part micro-electromechanical systems, or MEMS. The basic principle operating behind the MEMS accelerometer is the displacement of a small proof mass marked onto the silicon surface of the integrated circuit (IC) and suspended by small beams. As acceleration is applied to the device, a force develops which displaces the mass. Support beams act as a spring, and fluid (usually air) trapped inside the IC acts as a damper, resulting in a second-order lumped physical system.


In this study, accelerometers are used to acquire time history data to detect small vibration signals with good accuracy. It is chosen based on factors such as frequency response, sensitivity and noise tolerance. The details of the sensor are presented in Table 1.

2.2. Test configuration

For the field test, two accelerometers were located in an array for two types of configurations. In the first configuration, the accelerometers were positioned 0.15 m apart, and in the second configuration, the accelerometers were positioned 0.30 m apart. Both accelerometers were mounted with weights, as shown in Figure 2, to ensure good coupling between accelerometers and pavement surface. For the first configuration, three source distances, 0.15, 0.3 and 0.6 m, from the first receiver were used. For the second configuration, the sources were positioned 0.30, 0.6 and 1.2 m from the first receiver. Steel balls were used as a source and measurements were recorded for both configurations and for all source distances. The tests were carried out by dropping the steel balls from two different heights, 0.25 and 0.50 m. Figure 3 shows the distance layout of the receiver, the distance of the sources and height of the dropping balls. Input source energy is plotted in Joule, and is calculated using Equation (1):

$$\text{Energy} = mgh \quad (1)$$

where m is mass of the dropping ball (kg), g is the acceleration due to gravity (9.81 ms^{-2}) and h is height of fall of the ball (m).

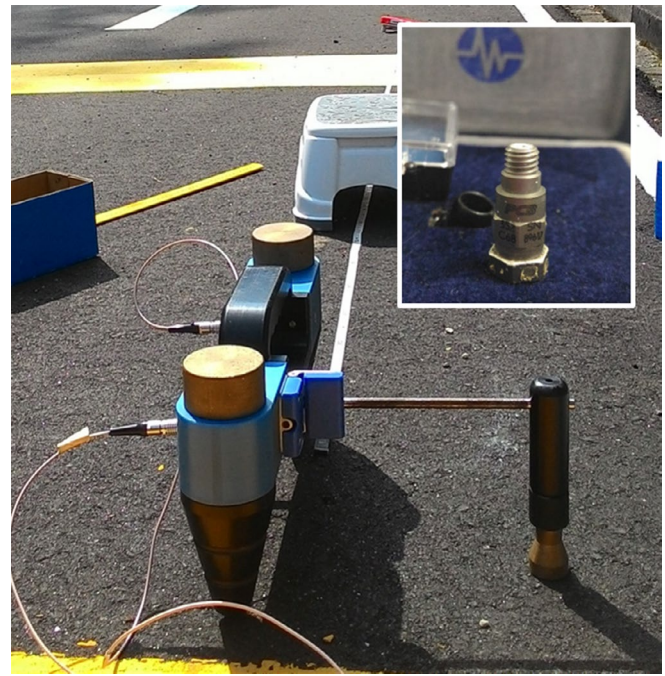**Figure 2.** Weight-mounted accelerometers used during measurement.

2.3. Numerical integration of acceleration

It is generally known that acceleration time history can be used to obtain displacement. This can be done by applying double integration to the acceleration data signal. Although theoretically it looks like a straightforward procedure, it is actually much trickier than it actually seems. The acceleration data signal must be firstly numerically integrated to obtain velocity, and thereafter numerically integrated again (this is the second integration) to obtain displacement. Numerical double integration of acceleration data signal involves errors that should be carefully studied and minimised. Errors could occur because, when integrating, low frequency contents of the waveform are greatly amplified, high frequencies are reduced and hence the phase is changed (Arraigada and Partl 2006). These problems, if not studied and handled properly, could affect and dominate the final result of the calculated displacement. In this paper, however, there is no frequency domain and hence no phase change. Also, a bandpass filter was applied during calculation to control the cut-off frequency accurately.

The displacement, velocity and acceleration parameters are closely related to one another (Arraigada and Partl 2006). Conversion can be done using the digital signal processing procedure by performing a single or double integration. Mathematically, displacement can be calculated from acceleration using Equation (2):

$$d_c(t) = d_0 + v_0 t + \int_0^t dt \int_0^\tau a(\tau) d\tau \quad (2)$$

where d_0 is initial displacement at $t = 0$, v_0 is initial velocity at $t = 0$ and d_c is calculated displacement at t .

It is known that the above equation is applied only for continuous (analog) function. Equation (3) can be used for a numerical

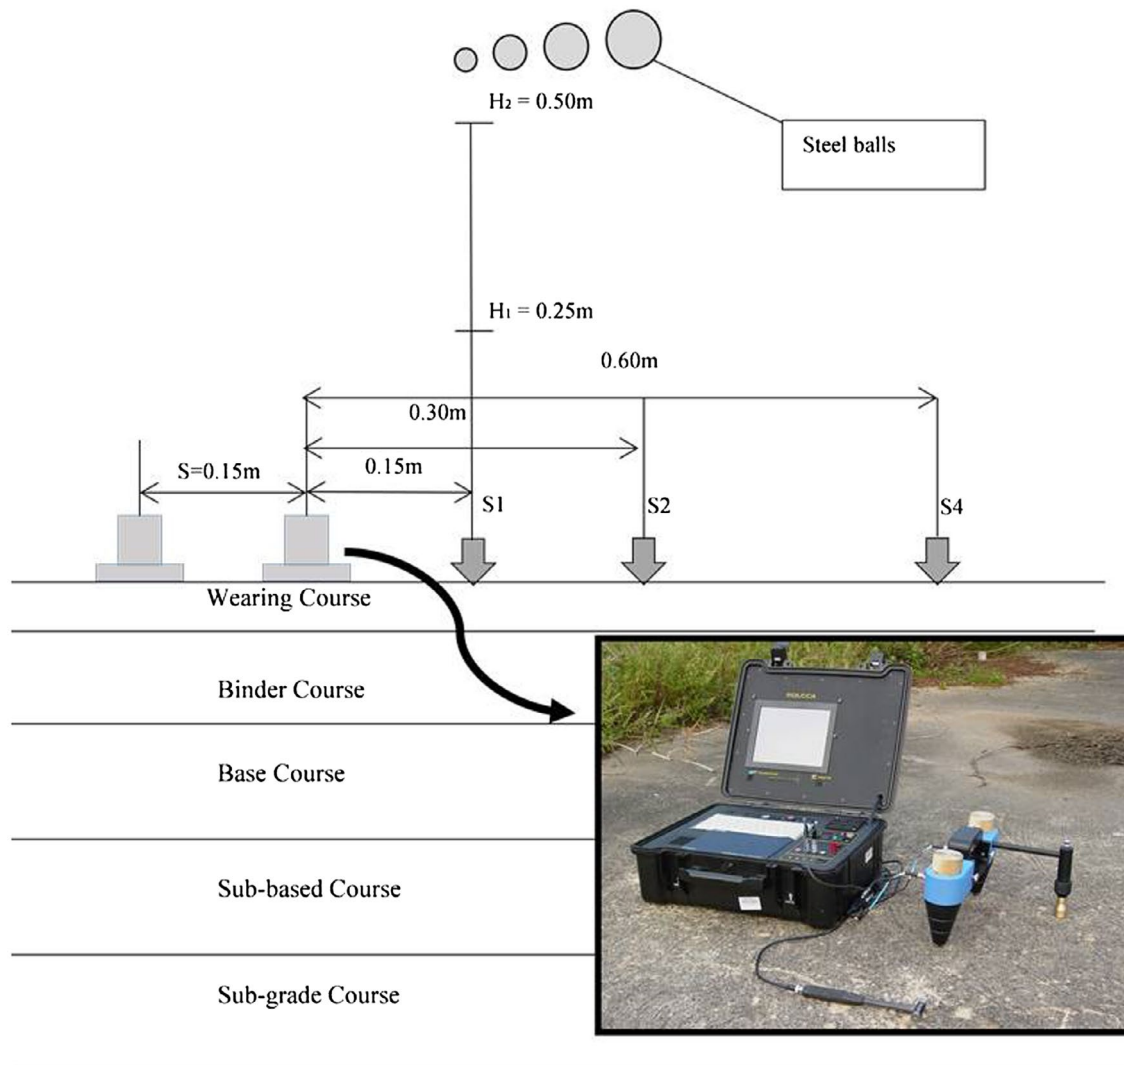


Figure 3. Layout of the SASW test configuration, with POLCCA.

integration (applied when the signal is discrete or digital) in the time domain:

$$\int_{t(0)}^{t(n)} a(t) dt \cong \sum_{i=1}^n \left(\frac{a(1-i) + a(i)}{2} \right) \Delta t \quad (3)$$

where $a(t)$ is continuous time domain waveform, $a(i)$ is i th sample of the time waveform, Δt is time increment between sample ($t(i) - t(i-1)$) and n is number of sample of the digital record.

Velocity then can be computed from the acceleration signal using Equation (4), and thereafter displacement can be calculated using Equation (5):

$$v_c(i) = v_c(i-1) + \frac{a(1-i) + a(i)}{2} \Delta t \quad (4)$$

and

$$d_c(i) = d_c(i-1) + \frac{v(1-i) + v(i)}{2} \Delta t \quad (5)$$

where $a(i)$ is i th sample of acceleration waveform, $v_c(i)$ is i th sample of calculated velocity and $d_c(i)$ is i th sample of calculated displacement.

In his paper, Joh (Joh *et al.* 2014) elaborated on velocity integration and its verification through laboratory tests such as LVDT measurements and potentiometer measurements. Numerical double integration is also discussed by Arraigada (Arraigada and Partl 2006) with verification of lab result from LVDT monitoring.

3. Results and discussion

3.1. Effect of input source energy

In order to obtain a reliable evaluation of stiffness profile, a single source and receiver set-up is not sufficient to determine the phase velocity over a wide range of wavelengths. Therefore, several measurement set-ups incorporating several source locations should be used. This source offset concept was used during field measurement. For a receiver distance of 0.15 m, the source offset is kept constant at 0.15, 0.30 and 0.60 m from the first receiver. The dispersion curve is a combination of three individual dispersion curves from three locations of source offset. Figure 4 shows the dispersion curves obtained using all four balls as sources with 0.15 m receiver distance, at dropping heights 0.25 and 0.50 m, respectively.

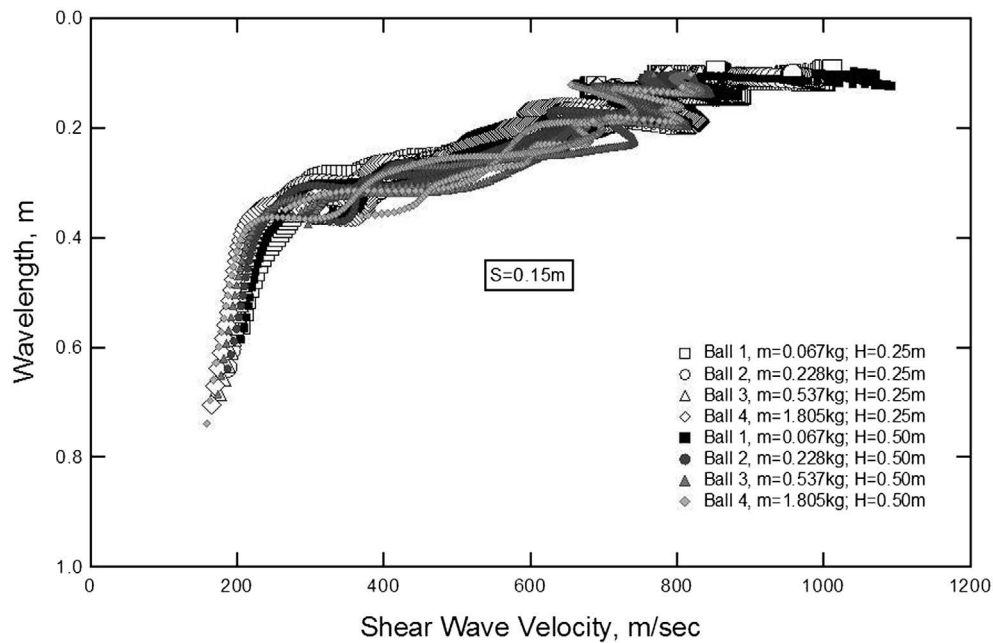


Figure 4. Dispersion curves from SASW measurements with 0.15 m receiver distance for height of dropping mass 0.25 and 0.50 m.

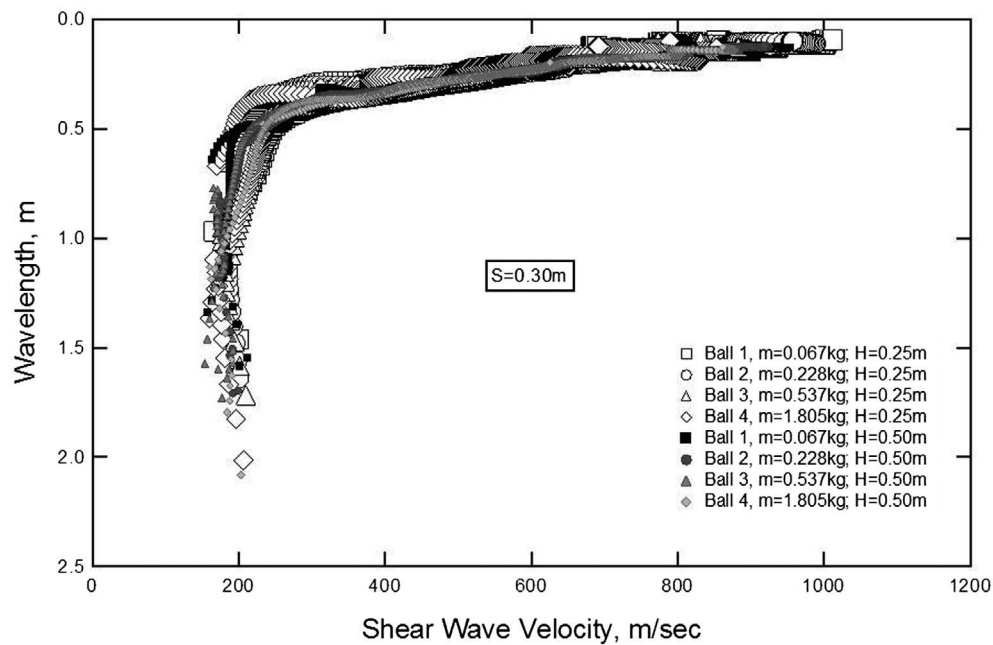


Figure 5. Dispersion curves from SASW measurements with 0.30 m receiver distance for height of dropping mass 0.25 and 0.50 m.

For a receiver distance of 0.30 m, the source offset is kept constant at 0.30, 0.60 and 1.2 m from the first receiver. Figure 5 shows the dispersion curves obtained using all four balls as sources with 0.30 m receiver distance, at both 0.25 and 0.50 m dropping heights. Both measurement set-ups are shown in Figures 4 and 5; the figures show that the increase in steel balls with larger mass or diameter yielded higher values of λ_{\min} and λ_{\max} .

It can also be proven that for both heights of dropping ball, the ball with the largest mass, namely Ball 4, produced the largest wavelength, and vice versa. Ball 4 not only has the highest mass but also the largest diameter, which means larger surface contact between the pavement surface and the steel ball. It therefore resulted in a

longer duration of contact time. Previous studies have shown that the duration of impact has a profound effect on the dominant spectral content of the emerging signal (Kumar and Hazra 2014a, 2014b, Barnes and Trotter 2009a, Barnes and Trotter 2009b). This has been distinguished in this research, as evident in both Figures 4 and 5, which shows that impacts of long duration generate low frequency signals which in turn result in deeper exploration depth. On the other hand, smaller balls generate high frequency signals which produced shorter duration impacts.

For the different heights of fall of the dropping mass, the values for λ_{\min} and λ_{\max} were obtained from the dispersion plots and these values are tabulated in Table 2 for a receiver distance of

Table 2. Comparison of λ_{\min} and λ_{\max} values for different drop heights of steel balls for a receiver distance of 0.15 m.

Ball no	Ball diameter (mm)	Height of fall, H (m)			
		0.25		0.50	
		λ_{\max} (m)	λ_{\min} (m)	λ_{\max} (m)	λ_{\min} (m)
1	25.40	0.5585	0.0939	0.5864	0.0979
2	38.10	0.6371	0.1012	0.6389	0.1013
3	50.80	0.6809	0.1025	0.6856	0.1028
4	76.20	0.7057	0.1029	0.7392	0.1032



Table 3. Comparison of λ_{\min} and λ_{\max} values for different drop heights of steel balls for a receiver distance of 0.30 m.

Ball no	Ball diameter (mm)	Height of fall, H (m)			
		0.25		0.50	
		λ_{\max} (m)	λ_{\min} (m)	λ_{\max} (m)	λ_{\min} (m)
1	25.40	1.4624	0.1024	1.5846	0.1207
2	38.10	1.6389	0.1211	1.7082	0.1215
3	50.80	1.7173	0.1291	1.7297	0.1295
4	76.20	2.0148	0.1300	2.0811	0.1306

0.15 m, and in Table 3 for a receiver distance of 0.30 m. Regardless of the receiver distance, either 0.15 or 0.30 m, height of fall of the dropping mass does not result in any significant change in the values of λ_{\min} and λ_{\max} . Tables 2 and 3 support this fact.

The source offset concept states that the first source is equal to the receiver distance; therefore, a longer receiver distance means that the source is located further away from the receiver. Rayleigh surface waves spread cylindrically from a point source and tend to dominate the measured wave field at large distance. In simpler terms, large receiver distance allows wavelength to penetrate deeper and therefore provide information of the subsurface in the lower frequency region. This study could serve as a guide in determining the proper configuration for obtaining data within the depth of interest of the pavement layer.

The differences in λ_{\min} and λ_{\max} with different input source energies are plotted exclusively for receiver distance 0.15 m and are shown in Figure 6 while Figure 7 shows the plot for receiver distance of 0.30 m. It can be seen that λ_{\max} increases linearly with an increase in the magnitude of input energy. This is true for both receiver distances. Figures 6 and 7 also show that λ_{\min} increases with an increase in the magnitude of input energy. In other words, contrary to the maximum

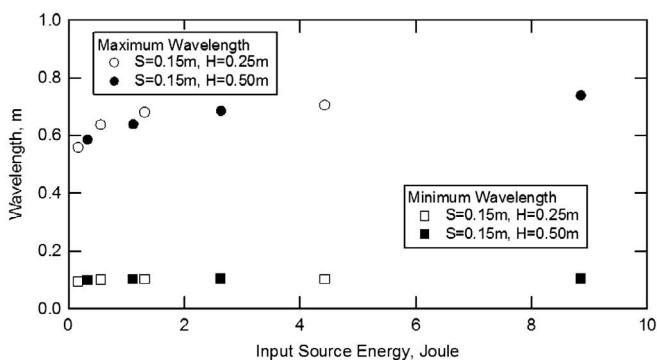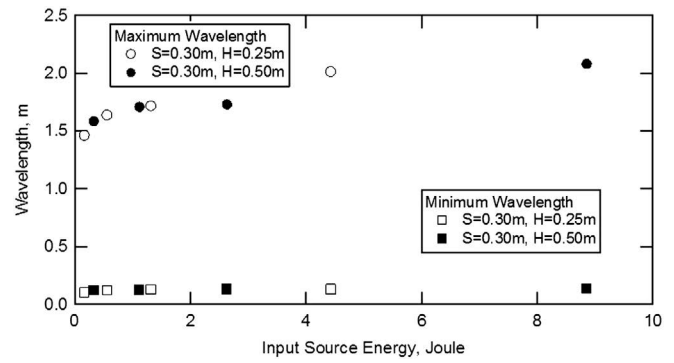**Figure 6.** The effect of changes in input energy on maximum wavelength (λ_{\max}) and minimum wavelength (λ_{\min}) for receiver distance, $S = 0.15$ m.**Figure 7.** The effect of changes in input energy on maximum wavelength (λ_{\max}) and minimum wavelength (λ_{\min}) for receiver distance, $S = 0.30$ m.

wavelength, the height of dropping mass and the mass of the steel ball do not have significant effect in the value of minimum wavelength.

Inversion analysis was also done to obtain the layer properties of the pavement. The shear wave velocity profiles of four cases were generated and are shown in Figure 8. SASW method uses the 'superposed' mode, which does not fall into specific normal modes (fundamental and higher modes). This is an important feature since for irregular pavement layering systems, these superposed/apparent phase velocities fall in between the normal modes. And since source location for pavement testing is also close to the receiver location, mode separation of surface wave is not practical (Stokoe *et al.* 2004). Therefore, for pavement testing, the SASW method, which incorporates superposed mode of higher mode surface waves and body waves, has a significant advantage over methods such as MASW and ReMi in terms of the application of modes for inversion analysis. The phase unwrapping procedure is also cumbersome in irregular pavement layering systems, but can be improved through signal processing technique called the Impulse Response Filtration (Stokoe *et al.* 2004).

3.2. Numerical integration of acceleration data to obtain displacement

Acceleration data are obtained from raw output voltage which is measured through acceleration sensitivity. Bandpass filtering was applied to acceleration data which was then integrated to obtain velocity. Filtration was done to remove high frequency noise and low frequency drift of the signals. Displacement was then obtained through analysis which is equivalent to integrating velocity signals after performing the filtration process. Figure 9 shows the acceleration time history obtained from Accelerometer 1 and its velocity after the first integration. The extracted data were from the measurement obtained from using Ball 4 as a source (refer to Figure 1). In the SASW method, the sensor/receiver located nearest to the source (where the load is applied) is called Accelerometer 1, while the second sensor/receiver located after the first one is named Accelerometer 2.

This makes sense since as the travelling time of the signal increases, more energy is dissipated and therefore the signal gets weaker as it reached the second sensor. This explains the higher

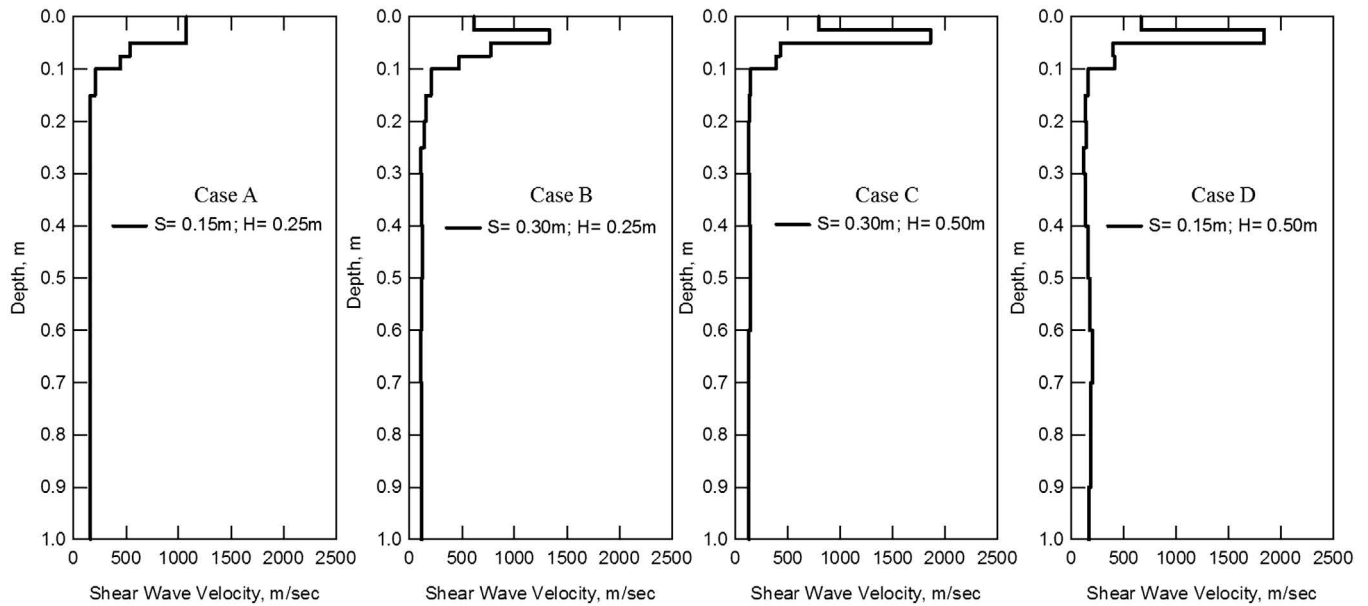


Figure 8. Shear wave velocity profiles generated for four cases: (1) Case A – receiver spacing, $S = 0.15$ m; height of falling weight, $H = 0.50$ m, (2) Case B – receiver spacing, $S = 0.15$ m; height of falling weight, $H = 0.25$ m, (3) Case C – receiver spacing, $S = 0.30$ m; height of falling weight, $H = 0.50$ m and (4) Case D – receiver spacing, $S = 0.30$ m; height of falling weight, $H = 0.25$ m.

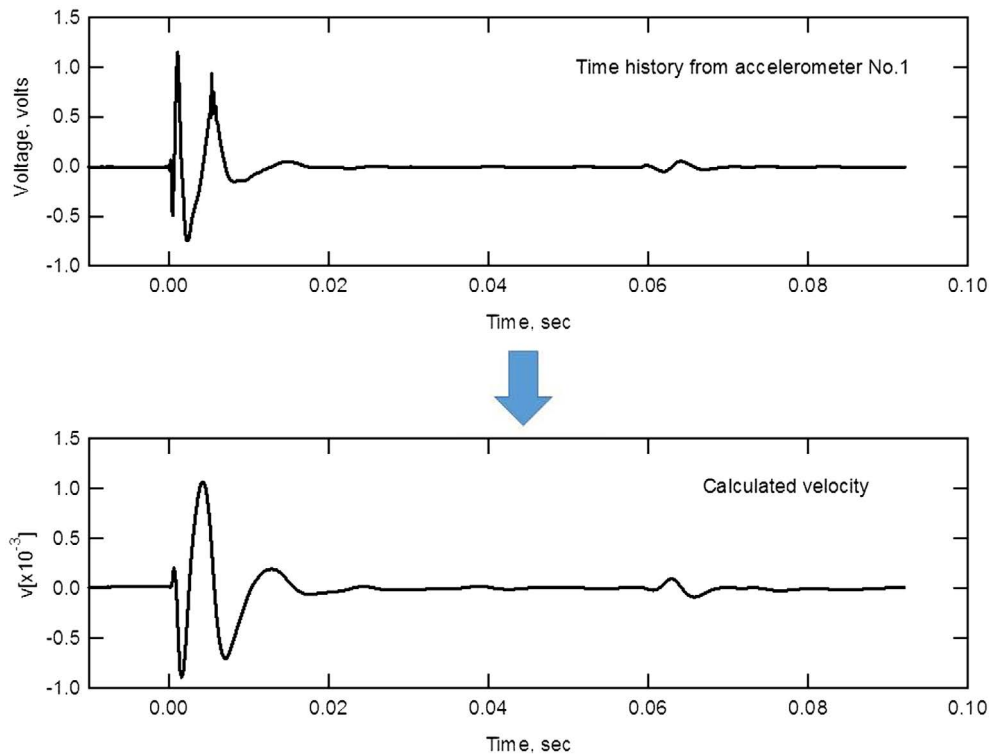


Figure 9. Calculated velocity obtained from acceleration time history recorded by accelerometer No 1.

amplitude of the signal recorded by Accelerometer 1 compared to the signal recorded by Accelerometer 2, as shown in Figure 10. Figures 9 and 10 show the velocity obtained from the first numerical integration of the acceleration signal. In this measurement record, the sampling rate is taken as 19 sample/s. The frequency span of the recorded data is 20 kHz. The time length recorded is 0.051175 s with 1024 frequency lines.

Displacement was then obtained by analysing and synthesising velocity data using Equations (2)–(5). The displacement obtained from the numerical double integration is shown in Figure 13 together with the displacement obtained through FEM. The figure will be discussed in the following section. The numerical integration produced good result, which is congruent with the displacement from FEM.

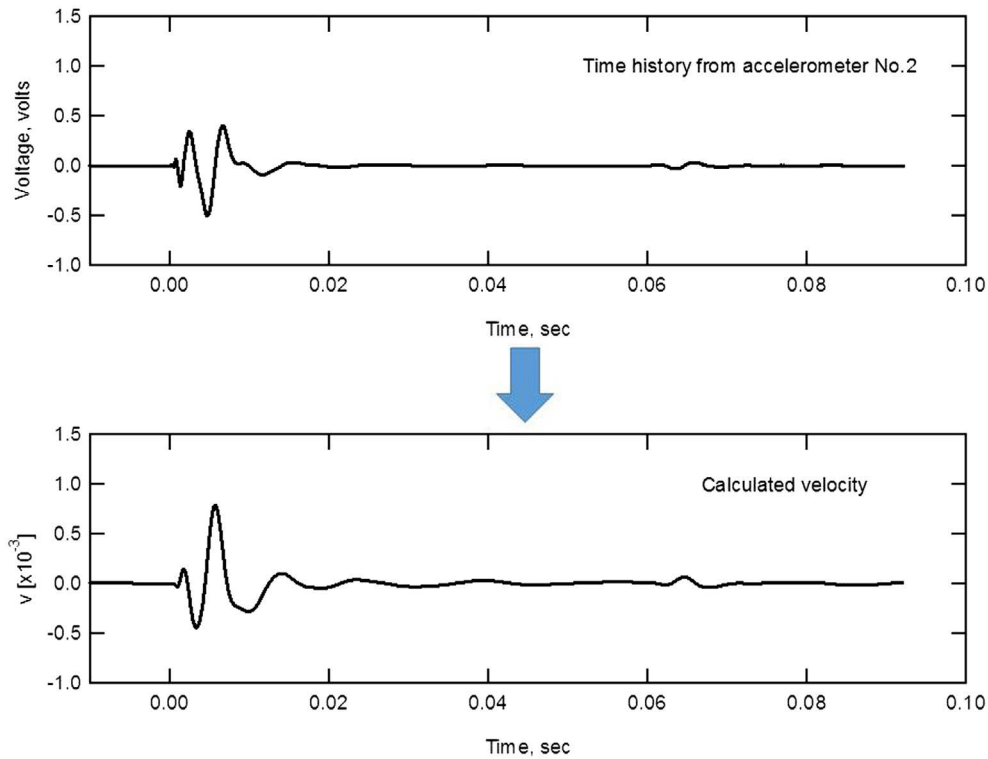


Figure 10. Calculated velocity obtained from acceleration time history recorded by accelerometer No 2.

3.3. Validation of displacement through finite element analysis

A model of layered pavement was built using commercial finite element analysis software called ABAQUS; it consists of a 0.10 m asphalt layer with a density of 2300 kg/m^3 , a 0.50 m base layer with a density of 2100 kg/m^3 and a 0.25 m sub-base layer with a density of 2100 kg/m^3 . The elastic moduli of the layers are 2500, 1000 and 500 MPa, respectively. The Poisson's ratio for asphalt layer is 0.35 while the base and sub-base layers share the same Poisson's ratio of 0.4. These parameters are in accordance with the specification set by The Department of Development Management and the Public Works Department (JKR 2008). The segment of the pavement layer and its characteristics are shown in Figure 11.

An impulse force of 17.7 N was applied to the pavement layer to obtain a structural response in terms of displacement. The change in momentum occurred at 0.017 s of period in time (during the impact), and assuming that there is no energy lost, the dropped mass is calculated to be 1.805 kg, which is the mass of Ball 4 (refer to Figure 1). Damping was neglected since very little energy was dissipated over a short period of time. The analysis was performed for a period of 0.105 s with a time increment of 1×10^{-7} second.

There are many factors contributing to the dynamic deformations of road, although according to Arraigada and Partl (Arraigada and Partl 2006), it is usually likely to find very small deformations at low frequencies. This happened because very little acceleration was recorded in the low frequency region. Figure 12 shows a sequence of pictures arranged to show the

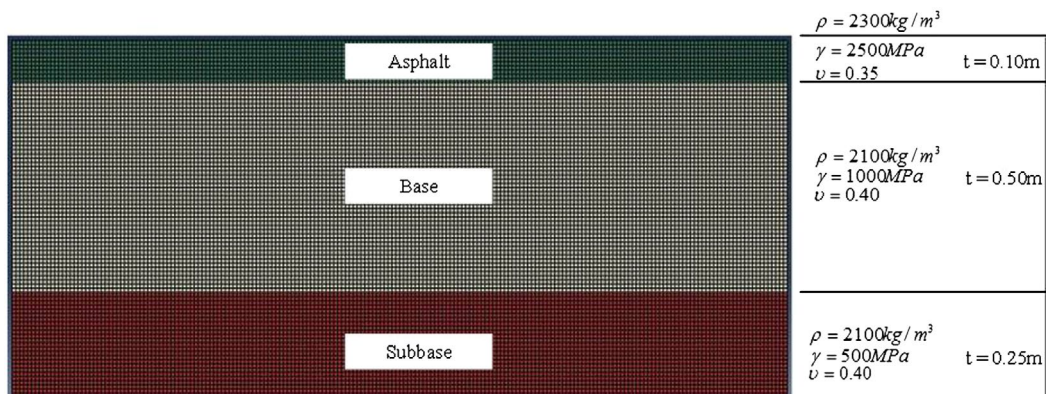


Figure 11. The model of pavement layer built in Finite Element Analysis' software.

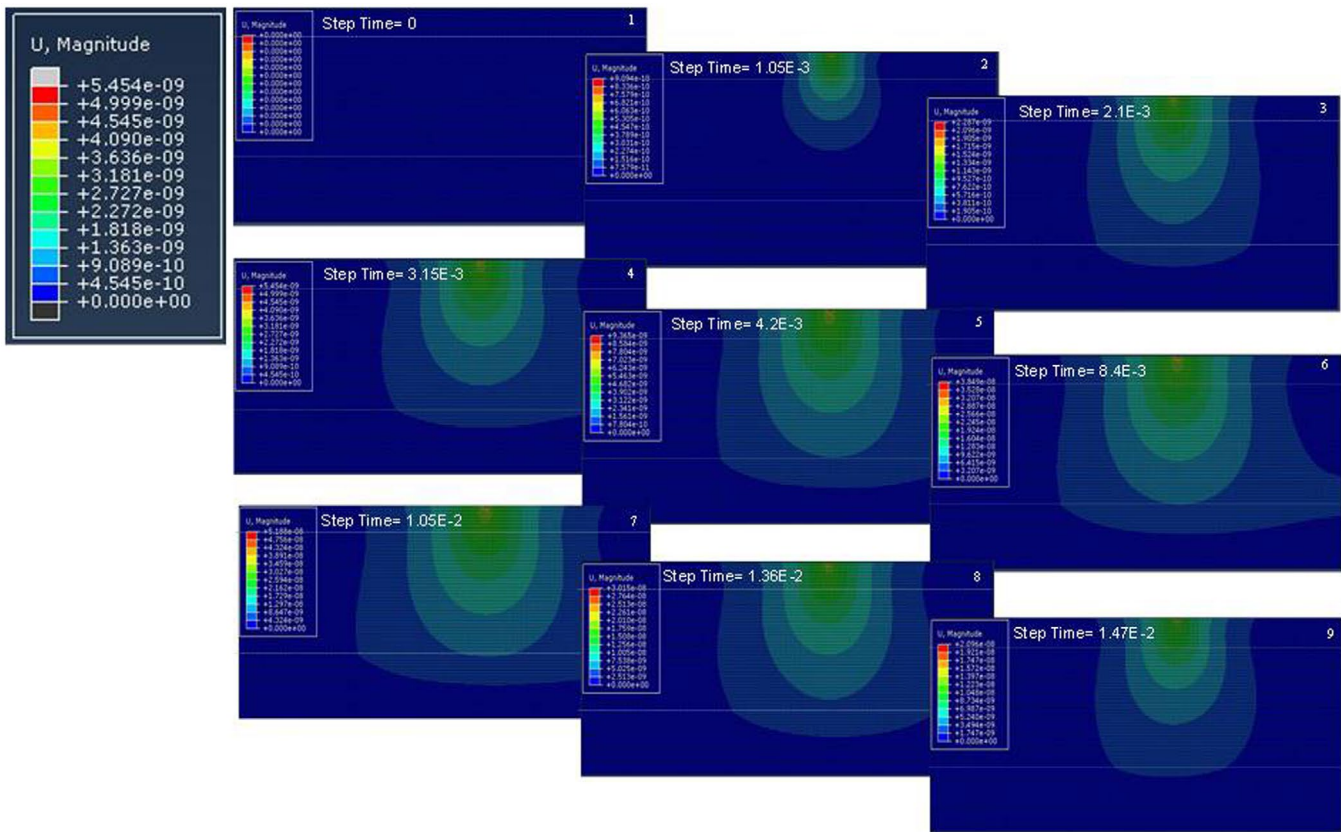


Figure 12. Picture in sequences from 1 to 9: deformation occurrence at the pavement layer model.

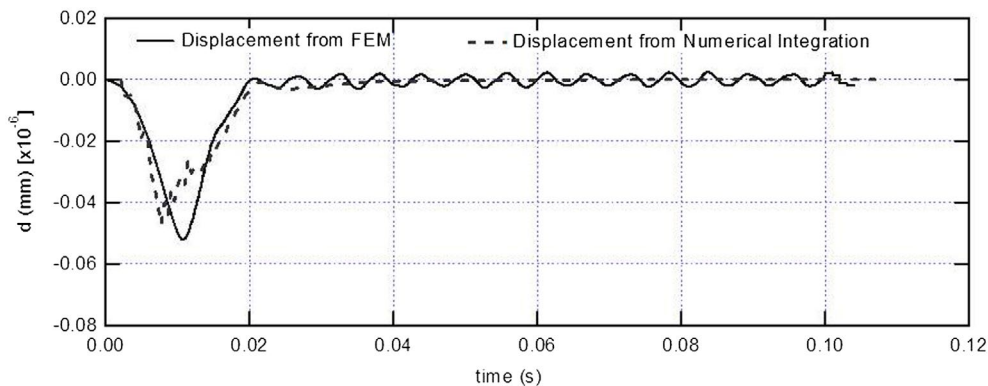


Figure 13. Comparison of displacement result obtained from numerical double integration and finite element analysis method.

occurrence of deformation in step motion during the period when the impulse force was applied to the model. Although the energy dissipates, the observed displacement was significantly small because the load applied was very small too.

The data collected post-analysis from the FEA software were plotted together with the displacement result obtained through velocity integration, and are shown in Figure 13. One apparent observation is that the displacement due to FEM resulted in lower valley compared to displacement due to numerical integration. This means that it has higher deflection. Other than that, the displacement result seems more stable during the impulse compared to the displacement obtained from numerical integration.

Peak difference could also occur because the integration procedure was adversely affected by the baseline offsets of the

sensors. However, as can be seen in the figure, the later signal is smoothed out when the numerical integration method was used compared to the FEM analysis. Although it is not very significant, this could be one of the advantages of the double integration procedure.

4. Conclusion

Based on SASW test done on asphaltic pavement, the effect of input source energy on the maximum wavelength (λ_{max}) and minimum wavelength (λ_{min}) was explored. The λ_{max} increases linearly with an increase in the input source energy due to the change in the height and the mass of the dropping ball; both these factors have a significant effect on the value of λ_{max} . It can

also be concluded that both the height and mass of the dropping ball have marginal effect on the value of λ_{\min} , as the result shows that its value is almost constant even when the magnitude of the input source energy was increased.

As stated in the earlier section of this paper, measurement of road deflection due to traffic loading could be done in a simple manner through the use of accelerometers. This, with the help of POLLCA, could provide many advantages, especially in terms of handling and mobility. It could be a low-cost solution for the measurement of road deflection in industry. The validity of using accelerometers as sensors to measure displacement was also verified using the finite element analysis software which gives good results when comparison was made. This study can be used as a guide for determining the receiver and array configuration in an SASW test on any pavement site. Researchers could also use accelerometers as sensors to evaluate road deflection.

Acknowledgement

The authors would like to express their sincere gratitude for their financial support and encouragement in conducting this research work.

Disclosure statement

No potential conflict of interest was reported by the authors.

Funding

The research was supported by research grant from the Ministry of Higher Education [grant number FRGS/2/2013/SG06/UKM/02/8] and National University of Malaysia (UKM).

ORCID

Amiruddin Ismail  <http://orcid.org/0000-0001-6547-8169>

References

- Arraigada, M. and Partl, M., 2006. Calculation of displacements of measured accelerations, analysis of two accelerometers and application in road engineering. *In: 6th Swiss transport research conference*, 15–17 March, Monte Verita/Ascona.
- Barness, C.L. and Trottier, J.F., 2009a. Evaluating high-frequency viscoelastic moduli in asphalt concrete. *Research in Nondestructive Evaluation*, 20 (2), 116–130.
- Barness, C.L. and Trottier, J.F., 2009b. Hybrid analysis of surface wave field data from Portland cement and asphalt concrete plates. *NDT & E International*, 42 (2), 106–112.
- Bowness, D., et al., 2007. Monitoring the dynamic displacements of railway track. *Proceedings of the Institution of Mechanical Engineers, Part F: Journal of Rail and Rapid Transit*, 221 (1), 13–22.
- Gucunski, N. and Woods, R.D., 1991. Instrumentation for SASW Testing. *In: Geotechnical Special Publication No 29. Recent Advances in Instrumentation, Data Acquisition and Testing in Soil Dynamics*. American Society of Civil Engineers, 1–16.
- Gucunski, N. and Woods, R.D., 1992. Numerical simulation of the SASW test. *Soil Dynamics and Earthquake Engineering*, 11, 213–227.
- Hall, L., 2003. Simulations and analyses of train-induced ground vibrations in finite element models. *Soil Dynamics and Earthquake Engineering*, 23, 403–413.
- Heisey, J.S., Stokoe, K.H. II, and Meyer, A.H., 1982. Moduli of pavement systems from spectral analysis of surface waves. *Transportation Research Record*, 852, 22–31.
- Jiang, H., et al., 2016. Simulating train moving loads in physical model testing of railway infrastructure and its numerical calibration. *Acta Geotechnica*, 11 (2), 231–242.
- Jiang, H., et al., 2016. Dynamic performance of high-speed railway formation with the rise of water table. *Engineering Geology*, 206, 18–32.
- Joh, S.-H., Rosenblad, B. L., and Stokoe II, K.H., 1997. Improved data interpretation method for SASW Tests at complex geotechnical sites. *International Society of Offshore and Polar Engineering*, 1, 875–881.
- Joh, S.H., et al., 2014. Alleviation of numerical instability in geophone-based measurement of track vibrations by utilizing a priori information. *KSCSE Journal of Civil Engineering*, 18 (5), 1351–1358.
- Jones, R., 1962. Surface wave technique for measuring the elastic properties and thickness of roads: theoretical development. *British Journal of Applied Physics*, 13 (1), 21–29.
- Kausel, E. and Roesset, J.M., 1981. Stiffness matrices for layered soils. *Bulletin of the Seismological Society of America*, 71 (6), 1743–1761.
- Kumar, J., 2011. A study on determining the theoretical dispersion curve for Rayleigh wave propagation. *Soil Dynamics and Earthquake Engineering*, 31 (8), 1196–1202.
- Kumar, J. and Hazra, S., 2014a. SASW testing of asphaltic pavement by dropping steel balls. *International Journal of Geotechnical Engineering*, 8 (1), 34–45.
- Kumar, J. and Hazra, S., 2014b. Effect of input source energy on SASW evaluation of cement concrete pavement. *Journal of Materials in Civil Engineering*, 26 (6), 1–7.
- Kumar, J. and Naskar, T., 2015. Effects of site stiffness and source to receiver distance on surface wave tests' results. *Soil Dynamics and Earthquake Engineering Journal*, 77 (1), 71–82.
- Kumar, J. and Rakaraddi, P.G., 2012. On the height of fall of dropping mass in SASW measurements for asphaltic road pavements. *International Journal of Pavement Engineering*, 13 (6), 485–493.
- Kumar, J. and Rakaraddi, P.G., 2013a. SASW evaluation of asphaltic and cement concrete pavements using different heights of fall for a spherical mass. *International Journal of Pavement Engineering*, 14 (4), 354–363.
- Kumar, J. and Rakaraddi, P.G., 2013b. Effect of source energy for SASW testing on geological sites. *Geotechnical and Geological Engineering*, 31 (1), 47–66.
- Lin, C.P. and Lin, C.H., 2007. Effect of lateral heterogeneity on surface wave testing: numerical simulations and a countermeasure. *Soil Dynamics and Earthquake Engineering*, 27, 541–552.
- Nazarian, S., 1984. *In situ determination of elastic moduli of soil deposits and pavement systems by spectral analysis of surface waves method*. Dissertation (PhD). The University of Texas.
- Nazarian, S. and Desai, M. R., 1993. Automated surface wave method: field testing. *Journal of Geotechnical Engineering*, 119 (7), 1094–1111. American Society of Civil Engineers.
- Nazarian, S. and Stokoe II, K. H., 1986. *In-situ determination of elastic moduli of pavement systems by spectral analysis of surface waves method (theoretical aspects)*. Austin: Centre for Transportation Research, University of Texas, Research Report 437-2.
- Nazarian, S. Stokoe II, et al., 1988. Determination of pavement layer thickness and moduli by SASW method. *Transportation Research Record*, 1196, 133–150.
- Priest, J.A. and Powrie, W., 2009. Determination of dynamic track modulus from measurement of track velocity during train passage. *Journal of Geotechnical and Geoenvironmental Engineering*, 135, 1732–1740.
- Rix, G. and Stokoe, K.H. II, 1989. Stiffness profiling of pavement subgrades. *Transportation Research Record*, 1235, 1–9.
- Roberts, G. W., Meng, X., and Dodson, A.H., 2001. The use of kinematic GPS and Triaxial accelerometers to monitor the deflections of large bridges. *In: International Federation of Surveyors (FIG) and Working Group 6.1 eds. Deformation measurements and analysis, 10th International symposium on deformation measurements*, 19–22 March. Orange, CA, 268–275.
- Roesset, J.M., 1998. Nondestructive dynamic testing of soils and pavements. *Tamkang Journal of Science and Engineering*, 1 (2), 61–81.
- Roesset, J. M., et al., 2011. Impact of weight falling onto the ground. *Journal of Geotechnical Engineering*, 120 (8), 1394–1412. American Society of Civil Engineers.

- Sayeed, M.A. and Shaheen, M.A., 2016. Three-dimensional numerical modelling of ballasted railway track foundations for high-speed trains with special reference to critical speed. *Transportation Geotechnics*, 6, 55–65.
- Simonin, J., *et al.*, 2009. Deflection measurement: the need of a continuous and full view approach. *In*: E. Tutumluer and I.L. Al-Qadi, eds. *Bearing capacity of roads, railways and airfields*. London: Taylor & Francis Group, 467–476.
- Stokoe II, K., *et al.*, 1994. Characterization of geotechnical sites by SASW method. *In*: R.D. Woods, ed. *Technical review: geotechnical characterization of sites* ISSMFE technical committee 10. New Delhi: Oxford.
- Stokoe II, K.H., Joh, S.H, and Woods, R.D., 2004. Some contributions of in situ geophysical measurements to solving geotechnical engineering problems. *In*: A. Viana da Fonseca and P.W. Mayne, eds. *Proceedings ISC-2 on geotechnical and geophysical site characterization*. Rotterdam: Millpress, 97–132.